

From the alloy design to the microstructural and mechanical properties of medium manganese steels of the third generation of advanced high strength steels

H. Essoussi ^{a,*}, S. Ettaqi ^a, E.H. Essadiqi ^b

* hamza.essoussi1@gmail.com

^a Laboratory of Energy, Materials and Sustainable Development, ENSAM, Moulay Ismail University, 15290, Meknes, Morocco

^b International University of Rabat, School of Aerospace & Automotive Engineering, LERMA Lab, Sala El Jadida, Morocco

(Received 01 June 2024; Accepted 13 November 2024)

Abstract

The automotive industry faces increasing pressure to reduce vehicle weight, enhance safety, and lower production costs while also complying with stricter environmental regulations. Various solutions have been developed to efficiently respond to these conflicting requirements. The promising solution involves the development of new steel types of the third-generation of advanced high-strength steels (3GAHSS), these steels aim to bridge the gap between TWIP and TRIP steels. The so-called (MM) Medium Manganese steels combining an exceptional strength, good malleability, with lower production costs attributed to the reduced use of alloying elements like manganese (below 12wt. %). The medium-Mn steel is drawing more attention to be designed for future vehicle bodies and structures. Therefore, this paper aims to explore the relationship between chemical composition, microstructure, manufacturing processes, and mechanical properties of Medium Mn steels.

Keywords: Medium Mn steels, Intercritical Annealing, Retained Austenite, Microstructure, Thermo-mechanical processing.

I- INTRODUCTION

The automotive industry faces the challenge of improving fuel efficiency and safety without increasing costs. For over 20 years, global automakers have been continuously researching material selection to reduce vehicle weight, minimize fuel consumption, and subsequently reduce CO₂ emissions. [1-6]. To response to these requirements, carmakers are constrained to use the most innovative solutions in terms of materials and design. Car body in white (BIW) and many other parts of vehicles are made of different materials. Hence there are two strategies for vehicle weight reduction: (i) Use permanently improved steel solutions; (ii) Use alternative materials such as aluminum, magnesium, plastics, and others [6],[7]. While Steels have the lowest environmental impact during production compared to other materials used for car bodies, in addition they are also easy to recycle because of their

magnetic properties, making them a sustainable choice for the automotive industry. For all these reasons, until now, steels stay very attractive and functional materials choice for car manufacturing because they offer a variety of mechanical properties and are affordable to produce. Ongoing research and development in steel technology is crucial for the automotive industry [4]. For many years, steel researchers were working on the first generation of Advanced High Strength Steels (AHSS) that includes the following grades: Dual Phase (DP), Transformation Induced Plasticity (TRIP), Complex Phase (CP) and Martensitic steels. Then, the Twinning Induced Plasticity (TWIP) steels, Al-alloyed lightweight steels with induced plasticity (L-IP) and Shear band strengthened steels (SIP) were discovered and investigated as the second generation of AHSS. However, high alloying cost, the difficulty in manufacturing process, the susceptibility to delayed fracture after forming and the relatively low yield strength all limit the immediate commercialization of the second generation steels. [1], [3], [8], [9], [10].

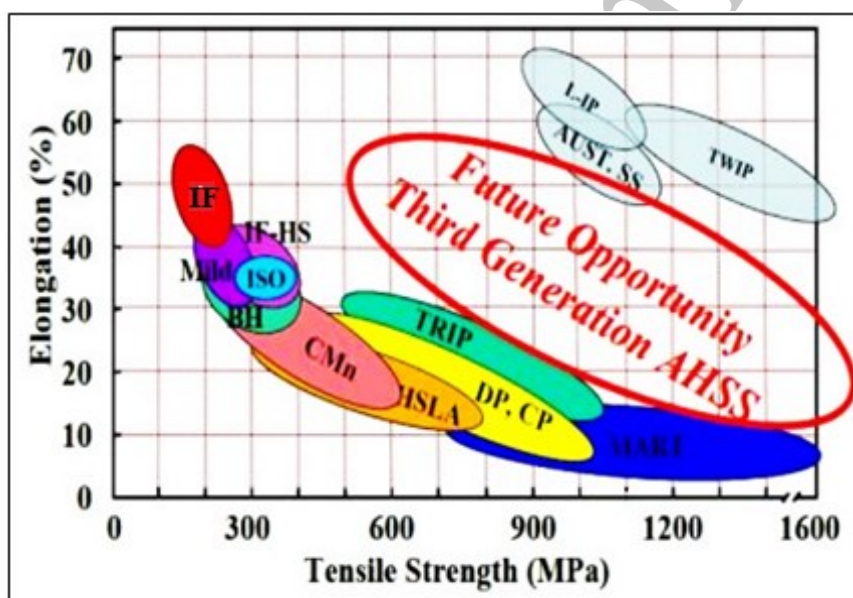


Figure.1: Schematic representation of tensile strength/total elongation balance for different already developed and future steels [6].

This leads to an increased interest in the development of the third generation of AHSS because they show a similar trade-off between strength and ductility as the second generation but have lower alloying cost and less difficulty on manufacturing. Most of the developed third generation steels are multi-phased, such as quenching and partitioning processed (Q&P), carbide free bainite (CFB), annealed martensite matrix (AMM) and medium Mn (MMS) steels [8], [9], [11], [12].

Medium Mn steels with Mn percentage in the range of 3% to 12 wt% is a promising solution to get high strength steels with good formability at lower alloying cost. This is primarily due to the enhanced TRIP effect resulted from a larger fraction of retained austenite with proper mechanic stability than the retained austenite in the classical TRIP steels. Recently many intense efforts have resulted in significant

progress on the development of medium Mn steels [6], [9-14]. A steel's formability, often measured by its energy absorption capacity, can be compared by multiplying its ultimate tensile strength (UTS) and total elongation (TE), resulting in a value known as PSE. Based on this PSE value, Advanced High Strength Steels (AHSS) are categorized into three generations (Fig. 1): first, second, and third. Figure.1 represents the relative positions of these generations. The first generation of Advanced High Strength Steels (AHSS) is characterized by with a product of strength and elongation (PSE) of 15 GPa%. These steels typically have a strength exceeding 800 MPa but limited elongation (less than 20%).while The second generation of AHSS has a PSE greater than 60 GPa%. The third generation of Advanced High Strength Steels (AHSS) exhibits a PSE value between 15 and 60 GPa%. In particular, our research is focused on the review of new designed medium Mn steels. Medium Mn steels with Mn percentage in the range of 3% to 12 wt% is a promising solution to get high strength steels with good formability at lower alloying cost. This is primarily due to the enhanced TRIP effect resulted from a larger fraction of retained austenite with proper mechanical stability than the retained austenite in the classical TRIP steels. Recently many intense efforts have resulted in significant progress on the development of medium Mn steels. Fig.2 summarizes the tensile properties of medium Mn steels that have been already reported [13-18]. These data scatter in a wide range as they are just simply classified according to the Mn content.

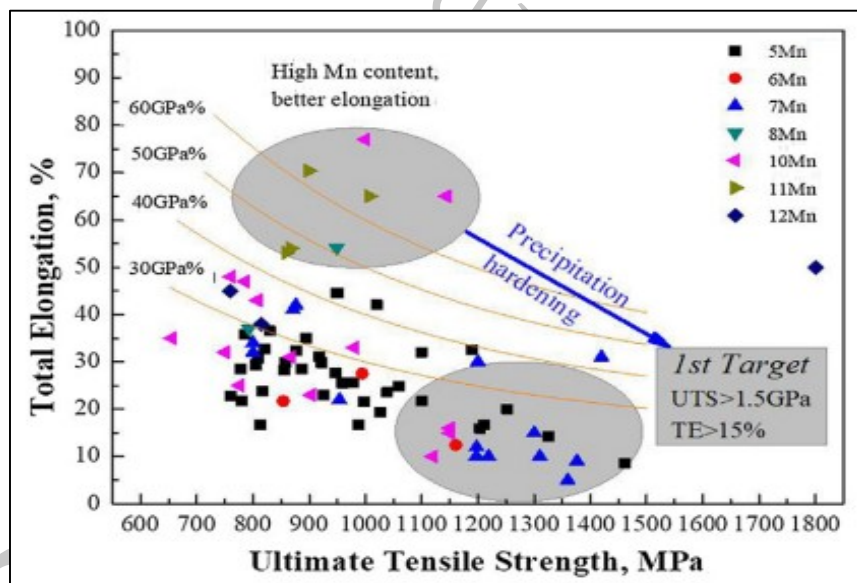


Figure.2 : Summary of tensile properties of medium Mn steels recently developed [6]

The mechanical properties of Medium Mn steels are very attractive, but there is a certain amount of unanswered question about microstructure formation, mechanical behavior and the link between these two properties, as well as the effect of processing routes and heat treatment on microstructure and mechanical properties.



Figure.3: Warm stamped B-pillars from medium-Mn steel [4]

Chang et al [4] introduced a warm stamping process for forming the B-pillar of a prototype car using medium-Mn steel at temperatures between 400°C and 700°C, optimized for optimal process parameters. Fully austenitized steel blanks were transferred to a high-speed hydraulic press and formed using a die with internal water-cooling channels. The parts were then quenched under constant holding pressure to achieve a fully martensitic microstructure. Notably, the medium-Mn parts exhibited uniform ultrafine morphologies throughout, regardless of whether the area was tension-dominated or compression-dominated. These steels exhibit exceptional strength-to-weight ratios, often surpassing conventional steels, this is due to the formation of unique multiphase microstructure composed of ferrite, bainite and retained austenite, which provide a balance of strength and toughness.

Therefore, this review focuses specifically on the relationship between the chemical composition, manufacturing process, multiphase microstructure, and mechanical properties of medium-Mn steels. The aim is to provide a comprehensive overview of how these factors influence the final properties of the steel. And By examining these factors and how they interact, the review aims to provide a deeper understanding of the underlying mechanisms that govern the behavior of medium-Mn steels. This knowledge can be valuable for developing new and improved steel alloys with tailored properties.

II- MEDIUM MN STEELS

1- Chemical composition

Medium Manganese (MM) steels are characterized by manganese content ranging from 3 to 10% and a complex microstructure consisting of ferrite, retained austenite, bainite, martensite, and small amounts of carbides. Although the concept of MM steels was first proposed by R.L. Miller in 1972 [20], it wasn't until 2007 that M.J. Merwin [21] reignited interest in these steels by refining the alloy composition for batch annealing processes. Just, after Merwin's work, various studies based on the medium Mn concept have been accelerated, at the beginning the large part of studies concentrated on the batch annealing using the simple Mn-C alloying system [14], [18]. While some of them were focused on understanding the effect of intercritical annealing conditions and alloying elements on the mechanical properties of these steels [22]. Carbon, manganese, silicon, and aluminum are the primary alloying elements found in most medium manganese steels [6]. Table. 1 provides a summary of the typical ranges of these elements and their corresponding effects on the steel.

Table 1: Alloying elements effects in Medium Mn steels

Alloying element	Effect
C	<ul style="list-style-type: none"> - Austenite stabilizer, the usual carbon content in medium Mn steels is in the range of 0.1-0.6 wt.% ; [6] - Increases the stability of the retained austenite; [23] - Increases the stacking fault energy; [24] - Higher C content may led to poor weldability; [9] - Higher C can cause severe carbon segregation during casting.[10], [25]
Mn	<ul style="list-style-type: none"> - As austenite stabilizer, the usual Manganese content in medium Mn steels is in the range of 3 to 10 wt.%; [26], [27] - At lower Mn content, low fraction of austenite retained and higher fraction of martensite are formed after intercritical annealing; [23] - High percentage of Mn in the retained austenite (RA) increases its stability; [28] - Decreases the stacking fault energy.[23]
Al	<ul style="list-style-type: none"> - Ferrite stabilizer, its concentration in medium Mn steels must not exceed 3wt.%; [6] - Inhibits the precipitation of cementite through increasing the carbides nucleation temperature; [14] - Excessive addition of Al leads to the formation of delta ferrite phase during solidification; [26], [29] - Improves weldability; [6] - Increases the stacking fault energy; [2], [30], [31].
Si	<ul style="list-style-type: none"> - Ferrite stabilizer, added in medium Mn steels with content less than 3wt.%; [2], [6], [24] - More than 3 wt.% Si addition can lead to the formation of a large fraction of δ-ferrite which remained coarse even after intercritical annealing;[32] - Leads to increased activity of C in ferrite, as well as makes carbon atoms can only be partitioned into austenite during intercritical annealing;[33] - Improves weldability; [6] - Decreases the stacking fault energy; [2], [30] - The excessive addition of Si may affect the surface quality and cause some difficulties in continuous casting, welding, surface coating and galvanizing. [6]

Micro-alloying elements like vanadium (V) and niobium (Nb) can be added to medium manganese (MM) steels to improve precipitation hardening and achieve sufficient ductility (greater than 15%) [6]. For instance, Hu et al [34] observed an increase in yield strength in an Fe-0.2C-6.5Mn-3Al-0.1V MM steel due to VC precipitation within the delta-ferrite phase after intercritical annealing. Similarly, Cai et al [35] developed an Fe-6.5Mn-1.1Al-0.17C MM steel with 0.22 wt% Mo and 0.05 wt% Nb, achieving an ultimate tensile strength of 1224 MPa and an elongation of 33%. This exceptional performance was attributed to their innovative micro-alloying strategy using molybdenum and niobium, which influenced austenite volume fraction and stability. S. Yan et al [36] discovered that adding copper and nickel to medium manganese steel not only increases the amount of retained austenite but also promotes the formation of numerous annealing twins during the annealing process. These twins contribute to breaking down and refining the austenite grains, leading to a significant increase in tensile strength of approximately 90-150 MPa.

2- Microstructural properties

Generally, Medium Mn steels are characterized by composite-like microstructure, while depending on the chemical composition and the processing routes, the final microstructure may be or Ferrite Martensite Duplex Phase (FMDP) as that can be seen in the case of Dual Phase (DP) steels [37], [38], Ferrite Austenite Duplex Phase (FADP) [39], or a mixture of these two types. In the case of FADP microstructure type, the Ultra Fine Grained (UFG) ferrite acts as matrix, with finely dispersed Retained Austenite (RA) islands, the volume fraction, size, morphology and stability of the retained austenite phase affect differently the final properties of these steels [40], [41], [42]. While, its stacking fault energy acts as a main parameter controlling the mode of deformation, can undergo changes due to the partitioning of alloying elements during intercritical annealing, C and Mn (austenite stabilizers) to austenite while Al and Si (ferrite stabilizers) to the ferrite [43] as described in Fig.4.

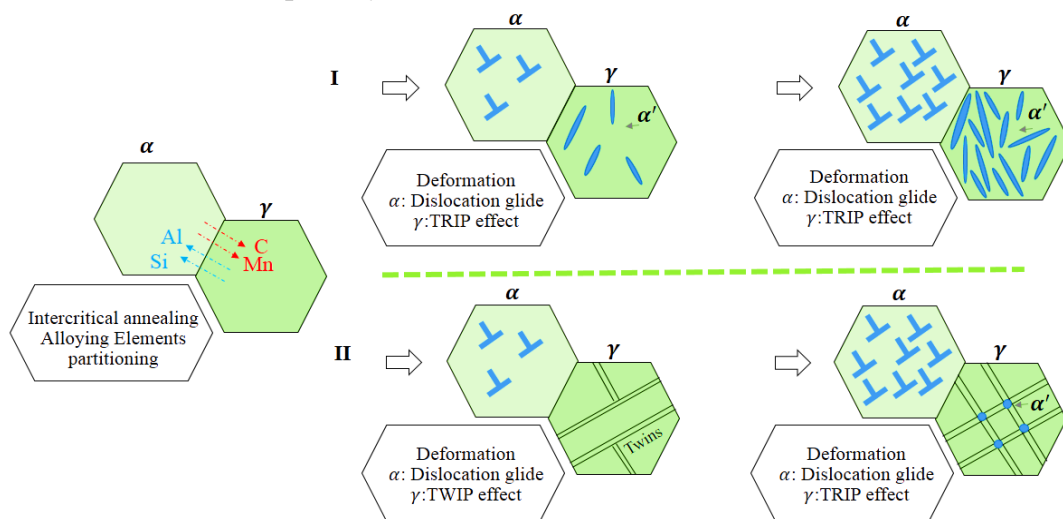


Figure.4: Schematic illustration of alloying elements partitioning taking place during intercritical annealing heat treatment [44]

The behavior of austenite grains during deformation depends on the stacking fault energy. In steels with low stacking fault energy, only transformation-induced plasticity (TRIP) occurs (Fig.4-I). However, in steels with medium stacking fault energy (Fig.4-II), both mechanical twinning (TWIP) and TRIP effects occur sequentially. Initially, twinning begins, followed by TRIP at twin boundaries as twinning progresses [44]. This combined effect of TWIP and TRIP enhances work hardening and ductility. Based on manganese content, medium manganese steels can be categorized into low and high manganese types, as summarized in Table.2.

Table.2: Overview of the main properties of the different types of medium Mn steels [45]

Medium Mn (MM)		
Category	High Mn	Low Mn
Wt.% of Mn	12-8	3-7
Applied Heat treatment	Intercritical annealing	
Cold rolled	Deformed α'	
After annealing	UFG $\gamma + \alpha + \alpha'$	
Plasticity	TWIP + TRIP	TRIP
$\gamma_{isf} (mJ/m^2)$	$15 < \gamma_{isf} < 45$	$\gamma_{isf} < 15$
RA-stability	Depends on the chemical composition, size and morphology of RA	

III- HEAT TREATMENT CONDITIONS EFFECT

Numerous studies [6], [45-49] have shown that intercritical annealing is a common method for producing medium manganese steels with high levels of retained austenite. Factors such as the specific alloying elements used [14], [33], [51], [52], the steel's initial structure, and the exact heat treatment conditions including heating and cooling rates [47], [53], holding times [47], [54], and annealing temperatures [55] can significantly influence the final microstructure of the steel.

1- Initial microstructure effect

The starting microstructure significantly influences how medium manganese steel changes during annealing. Particularly, comparing hot-rolled and cold-rolled steels after intercritical annealing reveals distinct differences. As shown in Fig.5, hot-rolled steel, which initially has a fully α' martensitic structure, transforms into a mixture of lath-shaped ferrite (α) and austenite (γ_R) after annealing. In contrast, cold-rolled steel with a deformed martensitic structure transformed into a microstructure containing globular ferrite and austenite after intercritical annealing. This observation aligns with the findings of J. Han et al [56] who compared the microstructures of intercritically annealed hot-rolled and cold-rolled Fe-9Mn-0.05C medium manganese steel. Their results showed a similar pattern of microstructural evolution. In the same scope, Xuan Li et al [57] observed a fine-grained, mixed structure of lamellar and equiaxed ferrite and austenite (40.5%) after intercritically annealing a cold-rolled Fe-

7.75Mn-2.78Al-0.52C medium manganese steel. This microstructure resulted from a combination of ferrite recrystallization and the reverse transformation of austenite.

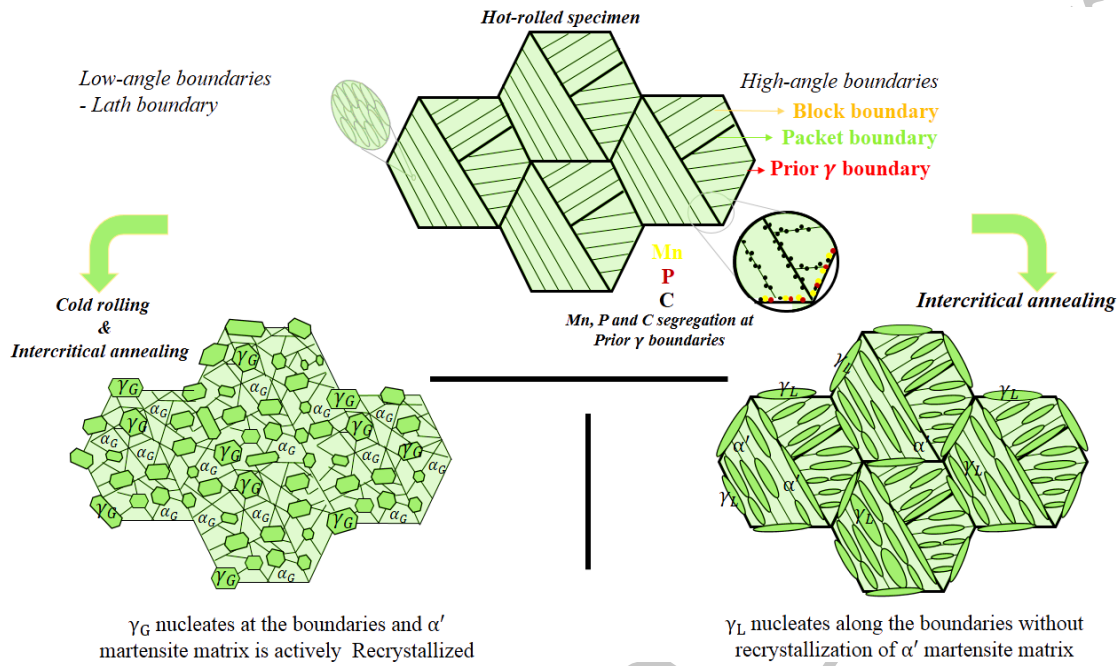


Figure.5: Schematic sketch of the difference between the cold and hot rolled specimens after intercritical annealing [58]

R. Zhang et al [59] introduced a new processing method for medium manganese steel (0.2C-5Mn wt.%), this process involves initial intercritical annealing followed by intercritical rolling at 650°C, resulting in a fine-grained, dual-phase microstructure with elongated ferrite and austenite grains aligned parallel to the rolling direction.

2- Heating rate effect

The rate at which a medium manganese steel is heated to its intercritical temperature significantly influences its final microstructure by affecting cementite formation and the stability of the reformed austenite. Han et al [60] studied this by comparing steels heated rapidly (diffusionless: Stage I of Fig.6) versus that slowly heated (diffusive: Stage II of Fig.6) to the intercritical temperature, The transition heating rate was approximately 15 °C/s . T_{θ} is the start temperature of cementite precipitation, and A_s and A_f are the start and finish temperatures of the reverse transformation, respectively.

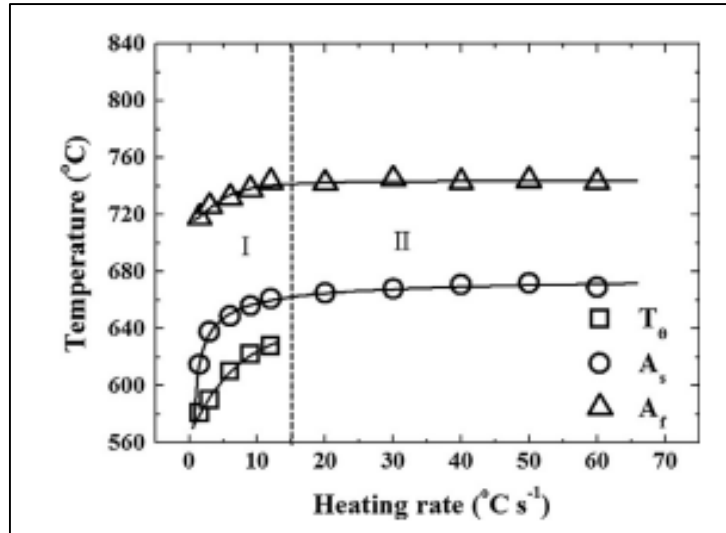


Figure.6: Change in the critical temperatures of both cementite precipitation and the reverse transformation as a function of the heating rate for the 9Mn-based specimens [60].

Their results revealed that rapidly heated steel contained lath-shaped retained austenite with many dislocations, while slowly heated steel had a more globular austenite with fewer dislocations. This difference is attributed to the lower chemical stability of the rapidly formed austenite.

3- Annealing temperature effect

Depending on the annealing temperature three scenarios can be obtained as illustrated in the sketch shown in Fig.7.

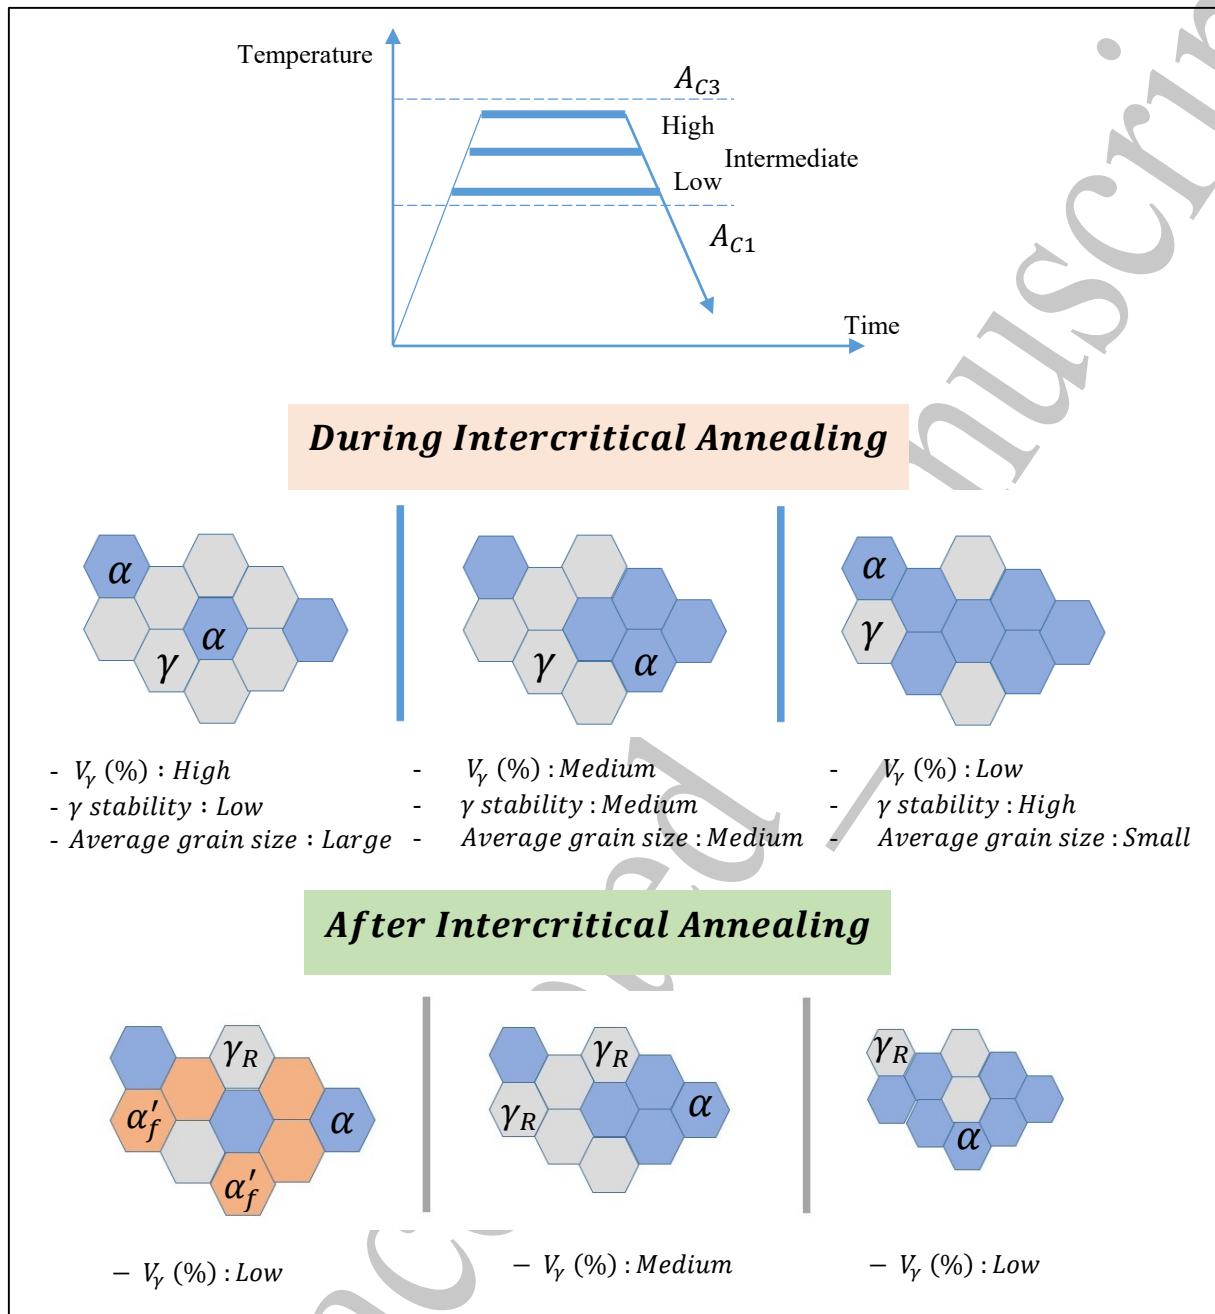


Figure.7: Sketch of microstructure evolution as function of intercritical annealing temperature: α is ferrite, γ is reverted austenite, γ_R is retained austenite and α'_f is fresh martensite [61]

As the annealing temperature is lowered (Fig.7), the amount of retained austenite decreases. Consequently, after cooling from low temperatures, the level of retained austenite is very low, but its stability is quite high [61]. On the other hand, when the intercritical annealing temperature is high, the amount of retained austenite increases. However, a large portion of the reverted austenite transforms into new martensite during cooling due to its instability. This results in a lower overall amount of retained austenite. Therefore, the optimal amount of retained austenite is achieved at a middle range

annealing temperature, where there's a good balance between the amount of retained austenite and its stability. This combination leads to the maximum amount of austenite remaining after cooling.

4- Annealing time effect

In medium manganese steels, the length of annealing time primarily affects the balance between the amount of retained austenite, grain size, alloy composition, and the stability of the reverted austenite. This influence is similar to that of annealing temperature. Based on research by W.Q. Cao et al [62] on Fe-0.2C-5Mn Medium Mn steel, it was found that extending the annealing time at 650°C for up to 144 hours results in an increased volume fraction of austenite. Additionally, the austenite grains become thicker and enriched with manganese. The amount of retained austenite steadily grows in proportion to the logarithm of annealing time, but this increase eventually stabilizes after 12 hours of annealing.

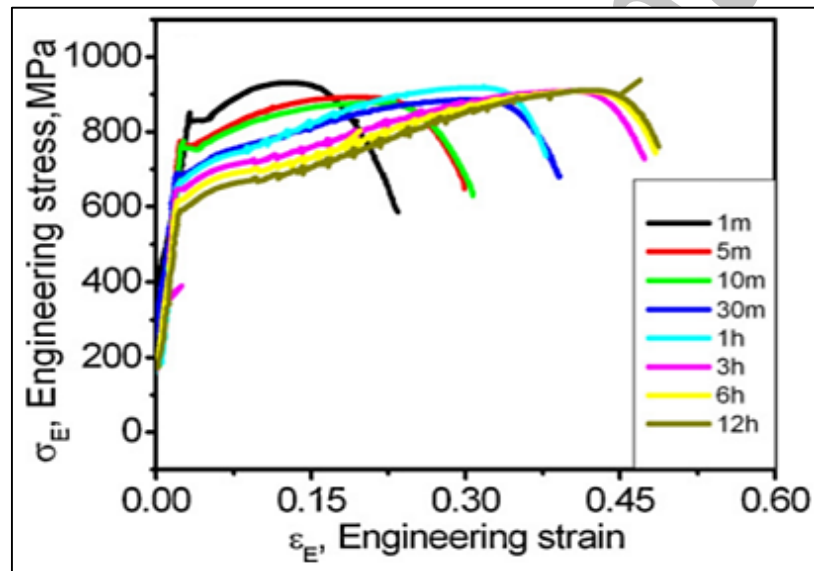


Figure.8: Effect of intercritical annealing time on the mechanical properties [62]

Therefore, the improved mechanical properties (Fig.8) especially the excellent combination of ultimate tensile strength (~ 960 MPa) and total elongation ($\sim 45\%$), were mainly due to the increased TRIP effect from the large fraction of austenite (34%) obtained after annealing for 6h at 650°C.

5- Cooling rate effect

The way a medium manganese steel is cooled after being heated and held at a constant temperature significantly affects its microstructure. A recent study by Furukawa et al [52] on various manganese steels found that those with more than 0.1% carbon were highly sensitive to cooling rates. For instance, Fe-5Mn-0.3C steel cooled rapidly in water retained a high amount of austenite (44.1%) while preventing the formation of carbides. In contrast, slower cooling in a furnace led to a much lower amount of retained austenite (31.2%) due to the formation of a significant quantity of cementite.

On the other hand, The impact of rapid cooling on the microstructure and mechanical properties of low-carbon, high-strength steel, annealed in the intercritical region, was studied by L. Zhuang et al [53] using a Gleeble 1500 thermomechanical simulator and a continuous annealing thermomechanical simulator, their results revealed that the microstructure primarily consisted of ferrite and bainite, with minor quantities of retained austenite and martensite islands forming at cooling rates of 5°C/s and 50°C/s respectively.

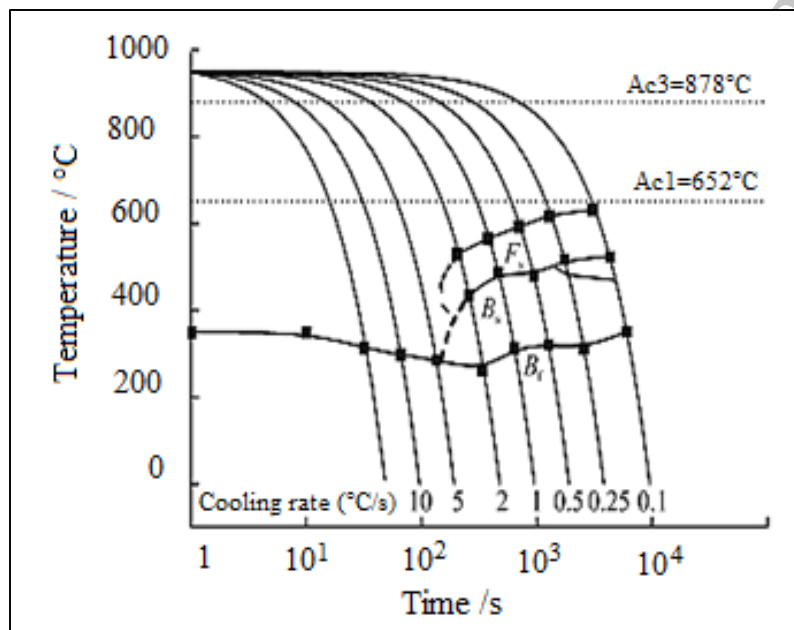


Figure.9: Continuous cooling transformation curve of the investigated steel [53]

The highest ultimate tensile strength (UTS) and yield strength (YS) of 1450 MPa and 951 MPa, respectively, were achieved for the sample cooled at a rate of 50°C/s. This is attributed to the dispersion strengthening effect of finer martensite islands (Fig.9), and the precipitation strengthening effect of carbide precipitates.

IV- MECHANICAL PROPERTIES OF MEDIUM MN STEELS

Several studies [42], [49], [63], [64], [65] have shown that medium manganese steels are prone to plastic instabilities. These instabilities can result in cracking during deep drawing or a rough surface that negatively impacts galvanizing. Common forms of plastic instability in these steels include Luders bands and the Portevin-Le Chatelier (PLC) effect. The occurrence of these instabilities is influenced by both internal and external factors. Internal factors include grain size, shape, dislocation density, and the concentration of elements like carbon and nitrogen [66]. External factors are strain rate and temperature. In the case of medium manganese steels, the transformation-induced plasticity (TRIP) and twinning-induced plasticity (TWIP) effects, as well as the stability of retained austenite, further contribute to the development of these plastic instabilities [65].

1- Luders bands in medium Mn steels

Luders bands are typically caused by static strain aging. They appear immediately after the initial plastic deformation, following the yield point drop, and continue through the plateau region of the stress-strain curve [65]. In medium manganese steels, this phenomenon is linked to manganese content. S. Lee et al [67] found that Luders strain increases as manganese concentration rises in intercritically annealed Fe-(5, 7, 9)Mn - 0.05C steels, as illustrated in Fig.10.

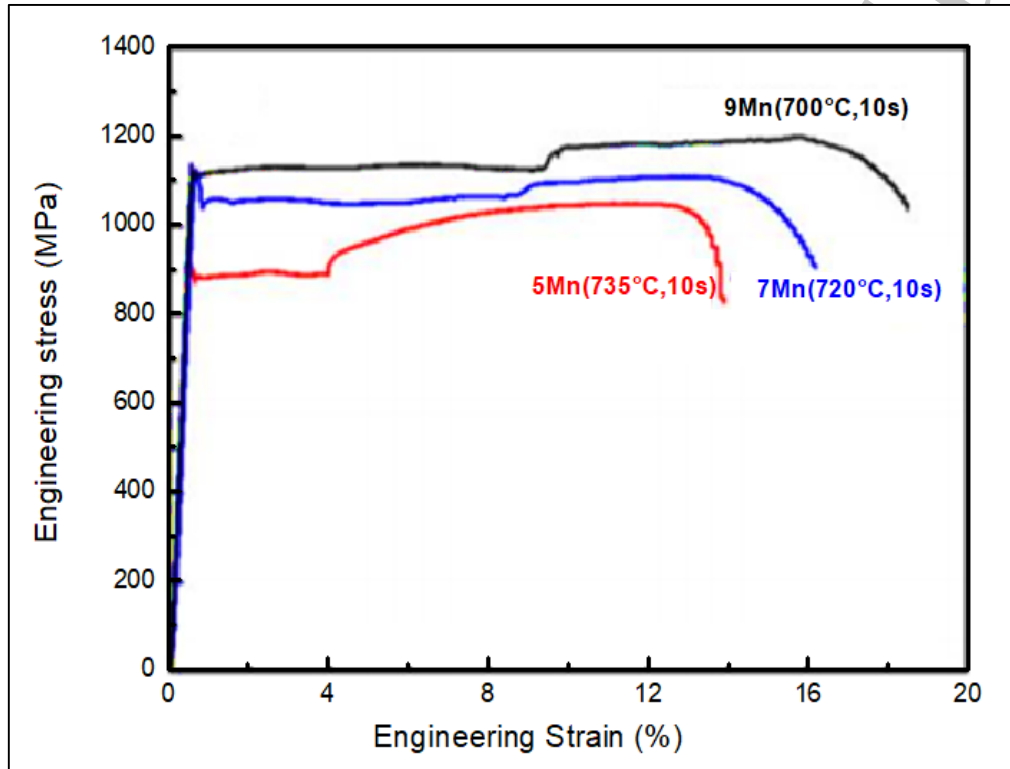


Figure.10: Engineering stress–strain curves of Fe-(5, 7, 9)Mn–0,05C (wt.%) cold rolled steels annealed for 10s at 735, 720 and 700°C respectively [67]

Eliminating Luders bands in medium manganese steels through heat treatment is challenging without compromising the material's mechanical properties. Research by Such et al [10] on Fe-6Mn-0.12C-0.5Si-3.1Al steel revealed that lower annealing temperatures result in a longer stress plateau. Conversely, higher annealing temperatures led to a shorter stress plateau, as depicted in Fig.11.

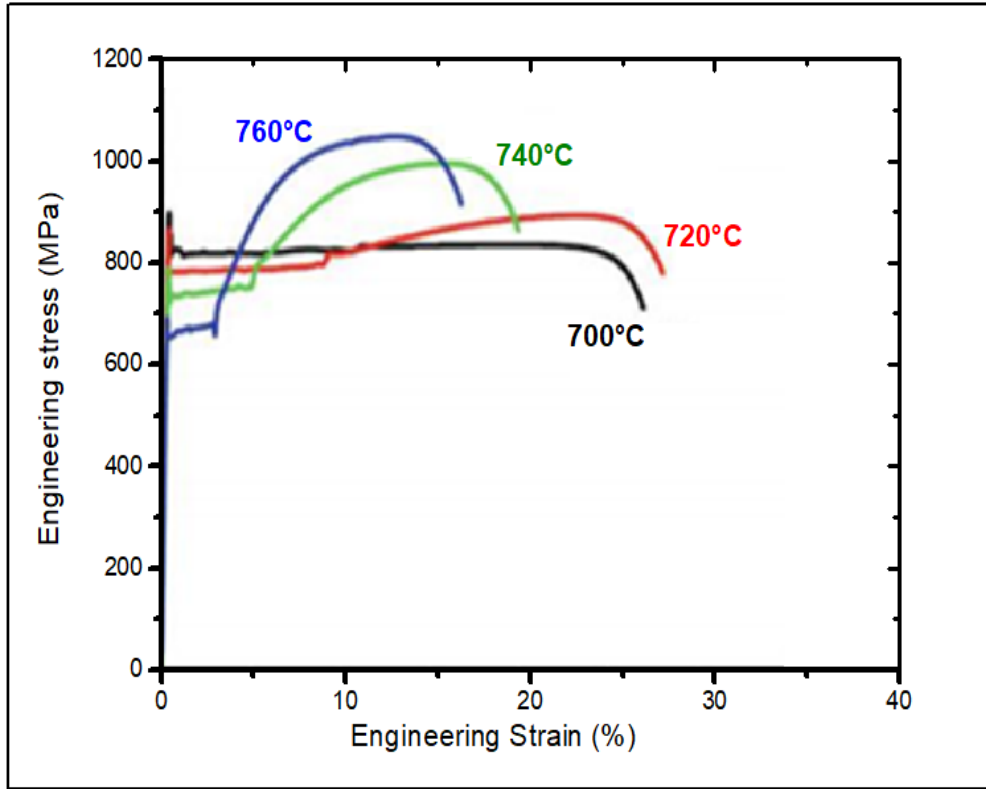


Figure. 11: Engineering stress–strain curves of Fe–6Mn–0.12C–0.5Si–3.1Al (wt-%) cold rolled steel annealed for 2 min tensile tests were performed at various intercritical annealing temperatures [10]

Conversely, regarding the deformation mechanisms at play, X.G. Wang et al [42] found through energy analysis of cold-rolled Fe-7Mn-0.14C-0.23Si medium manganese steel that strain-induced martensite formation primarily occurs within Luders bands, with minimal formation observed in Portevin-Le Chatelier (PLC) effect.

2- PLC effect in medium Mn steels

The PLC effect in polycrystals is typically categorized into three types (or a combination of them) based on the spatial arrangement of local deformation bands and the specific shape of the stress-strain curve. As the strain rate increases from the lower limit of plastic instability, a progression of PLC effect types can be observed, reflecting an increasing correlation between the deformation bands: random nucleation bands (Type C) transitioning to relay-racing-style bands (Type B), and ultimately to the propagation zone (Type A) [68]. Unlike Luders bands, Portevin-Le Chatelier (PLC) bands are associated with dynamic strain aging (DSA). They manifest as distinctive saw-tooth patterns on the stress-strain curve. Various theories explain the serrated flow behavior in steels. The most widely accepted explanation involves the interaction between solute atoms (like carbon) and moving dislocations, a concept originally introduced and subsequently refined by Cottrell [69], [49], [70]. Unlike traditional steels, medium manganese steels exhibit complex behaviors like TRIP and TWIP and have multi-phase microstructures. This makes understanding the Portevin-Le Chatelier (PLC) mechanism in these steels

particularly challenging. Consequently, there are limited studies exploring the nature of plastic instability in this type of steel. Yang et al [71] found that PLC bands in intercritically annealed 0.22C-7.2Mn-2.4Al medium manganese steel only form within austenite grains. This is attributed to the higher carbon content in the retained austenite compared to ferrite. Similarly, Sun et al [65] linked the occurrence of PLC serrations to strain-induced martensitic transformation in 0.2C-11.6Mn-2.7Al medium manganese steel.

PLC bands represent localized areas of strain where metastable austenite grains are prone to transforming into martensite due to intense stress, as reported in [71], [72]. Additionally, the influence of twinning-induced plasticity on PLC bands is similar to that observed in TWIP steels, primarily linked to the interaction of carbon-manganese pairs with dislocations during deformation, as described by A. Kozłowska et al [49]. Furthermore, the manufacturing process applied to these steels significantly impacts the occurrence of plastic instabilities. Hot-rolled medium manganese steels only exhibit Portevin-Le Chatelier (PLC) bands, with no evidence of discontinuous yielding. In contrast, both Luders bands and PLC effects can be observed in cold-rolled, then intercritically annealed medium manganese steels, as shown in Fig.12.

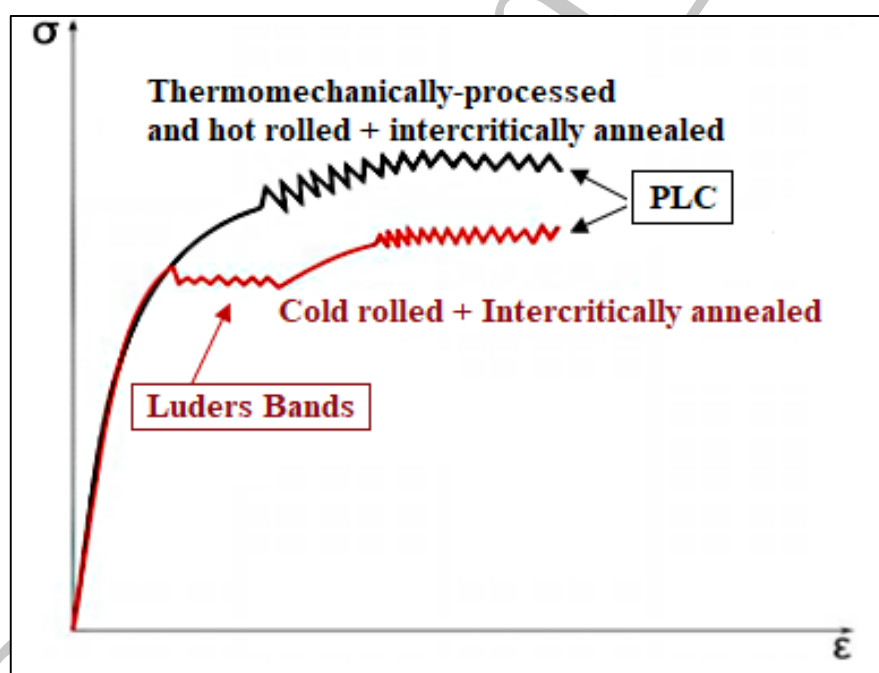


Figure.12: Types of plastic instability in medium-manganese steels [49]

Conversely, Y. Wang et al [73] investigated the relationship between cementite formation and the Portevin-Le Chatelier (PLC) effect in a hot-rolled medium manganese steel. They concluded that the formation of carbides significantly reduces the PLC effect by lowering the concentration of interstitial atoms in the steel's structure.

V- CONCLUSION

This review examines how the microstructure of medium manganese steels changes based on the initial chemical composition and different processing methods including hot and cold rolling, as well as under heat treatment conditions like heating rate, cooling rate, annealing temperature, and holding time. Therefore from the analysis of some previous works the main conclusions may be drawn here are:

- Austenite stability in medium Mn steels depends on multiple conditions: chemical composition, deformation mode, annealing temperature, and processing conditions.
- To fully benefit from the advantages of medium manganese steels, it is essential to understand the effect of each processing condition on the austenite stability;
- Austenite stability is a crucial factor in determining the mechanical properties of medium manganese steel mainly consisting of ferrite and austenite. During the deformation process, the phase composition undergoes dynamic changes, and the nucleation and expansion of the PLC band are closely linked to the distribution of phases in medium manganese steel.

Declaration of competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Funding

No funding was received for this work.

Abbreviation list :

- **AHSS** : Advanced High Strength Steels;
- **3GAHSS** : Third Generation of Advanced High Strength Steels;
- **BIW** : Body In White;
- **CP** : Complex Phase;
- **DP** : Dual Phase;
- **DSA** : Dynamic Strain Aging;
- **FMDP**: Ferrite Martensite Duplex Phase;
- **FADP** : Ferrite Austenite Duplex Phase;
- **IA** : Intercritical Annealing;
- **L-IP** : Lightweight -Induced Plasticity;
- **MM** : Medium Mn;

- **PLC** : Portevin-Le Chatelier;
- **PSE** : Product of Strength and Elongation;
- **RA**: Retained Austenite;
- **S-IP** : Shear-Induced Plasticity;
- **TE** : Total elongation;
- **TRIP** : Transformation Induced Plasticity;
- **TWIP** : Twinning Induced Plasticity;
- **UFG** : Ultra Fine Grained;
- **UTS** : Ultimate Tensile Strength;

References

- [1] H. Aydin, I.-H. Jung, E. Essadiqi, S. Yue, Twinning and Tripping in 10% Mn steels, *Material. Science Engineering A*, 591 (2014) 90-96, doi: 10.1016/j.msea.2013.10.088.
- [2] H. Essoussi, S. Ettaqi, E. Essadiqi, On the Prediction of Stacking Fault Energy on Medium MN Steels, *Physics of Metals and Metallography*, 122 (14), (2021), 1507-1512., doi: 10.1134/S0031918X21140076.
- [3] H. Choi, S. Lee, J. Lee, F. Barlat, B. C. De Cooman, Characterization of fracture in medium Mn steel, *Material. Science Engineering A*, 687, (2017), 200-210, doi: 10.1016/j.msea.2017.01.055.
- [4] Y. Chang, C. Y. Wang, K. M. Zhao, H. Dong, J. W. Yan, An introduction to medium-Mn steel: Metallurgy, mechanical properties and warm stamping process, *Materials & Design.*, 94, (2016) 424-432, doi: 10.1016/j.matdes.2016.01.048.
- [5] H. Essoussi, S. Ettaqi, On the mechanical properties of Al/Cu-grid/Al intermetallic composite », *Journal of Metals, Materials and Minerals*, 31 (2021), doi: 10.55713/jmmm.v31i1.1054.
- [6] B. Hu, H. Luo, F. Yang, H. Dong, Recent progress in medium-Mn steels made with new designing strategies, a review, *Journal of Materials Science & Technology*, 33 (12) (2017) 1457-1464, doi: 10.1016/j.jmst.2017.06.017.
- [7] G. Khalaj, H. Pouraliakbar, N. Arab, M. Nazerfakhari, Correlation of passivation current density and potential by using chemical composition and corrosion cell characteristics in HSLA steels, *Measurement*, 75 (2015) 5-11, doi: 10.1016/j.measurement.2015.07.048.
- [8] N. Khodaie, D. G. Ivey, H. Henein, Unit cell dilation technique for analyzing dilatometry data in microalloyed steels, *Materials. Characterization.*, 135 (2018) 84-95, doi: 10.1016/j.matchar.2017.11.020.
- [9] D.-W. Suh, S.-J. Kim, Medium Mn transformation-induced plasticity steels: Recent progress and challenges, *Scripta Materialia* 126 (2017) 63-67, doi: 10.1016/j.scriptamat.2016.07.013.
- [10] D. W. Suh, J. H. Ryu, M. S. Joo, H. S. Yang, K. Lee, H. K. D. H. Bhadeshia, Medium-Alloy Manganese-Rich Transformation-Induced Plasticity Steels, *Metallurgical and Materials Transactions A*, 44 (1) (2013) 286-293, doi: 10.1007/s11661-012-1402-3.
- [11] O. Angelo, C. Martin, M. Carlos, S. Juan Pablo, T. Victor, M. Manuel, R. David, Influence of martensite and grain size on the mechanical behavior of austenitic Fe–C–Mn–Ni–Al medium Mn steels with TWIP mechanism under uniaxial tension/compression and micromechanical creep, *Materials Chemistry and Physics*, 328 (2024) 129966, doi: 10.1016/j.matchemphys.2024.129966.
- [12] X. Li, Y. Chang, C. Wang, P. Hu, H. Dong, Comparison of the hot-stamped boron-alloyed steel and the warm-stamped medium-Mn steel on microstructure and mechanical properties, *Material. Science Engineering A*, 679 (2017) 240-248, doi: 10.1016/j.msea.2016.10.045.
- [13] G. Tian, J. Xiao, L. Yan, S. Yao, Z. Bao, A. Zhao, Preparation of high-strength and high-ductility medium Mn steel with chemistry heterogeneous via a two-step intercritical annealing process, *Journal of Materials Research and Technology*, 32 (2024) 1620-1629, doi: 10.1016/j.jmrt.2024.08.007.

- [14] D.-W. Suh, S.-J. Park, T.-H. Lee, C.-S. Oh, S.-J. Kim, Influence of Al on the Microstructural Evolution and Mechanical Behavior of Low-Carbon, Manganese Transformation-Induced-Plasticity Steel, *Metallurgical and Materials Transactions A*, 41 (2) (2010) 397-408, doi: 10.1007/s11661-009-0124-7.
- [15] S.Chang-Hyo, K.K.Hyuk, C.kayoung, K.Kyung-Hun, Kwak.J.H, S.Lee, K.NackJ, Deformation behavior of ferrite–austenite duplex lightweight Fe–Mn–Al–C steel, *Scripta Materialia*, 66 (8) (2012)519-522, doi: 10.1016/j.scriptamat.2011.12.026.
- [16] S.-J. Park, B. Hwang, K. H. Lee, T.-H. Lee, D.-W. Suh, H. N. Han, Microstructure and tensile behavior of duplex low-density steel containing 5 mass% aluminum », *Scripta Materialia*, 68 (6) (2013) 365-369, doi: 10.1016/j.scriptamat.2012.09.030.
- [17] O. Bouaziz, S. Allain, C. P. Scott, P. Cugy, D. Barbier, High manganese austenitic twinning induced plasticity steels: A review of the microstructure properties relationships, *Current Opinion in Solid State and Materials Science*, 15 (4) (2011) 141-168, doi: 10.1016/j.cossms.2011.04.002.
- [18] P. J. Gibbs, E. De Moor, M. J. Merwin, B. Clausen, J. G. Speer, D. K. Matlock, Austenite Stability Effects on Tensile Behavior of Manganese-Enriched-Austenite Transformation-Induced Plasticity Steel, *Metallurgical and Materials Transactions A*, 42 (12) (2011) 3691-3702, doi: 10.1007/s11661-011-0687-y.
- [19] C.-Y. Lee, J. Jeong, J. Han, S.-J. Lee, S. Lee, Y.-K. Lee, Coupled strengthening in a medium manganese lightweight steel with an inhomogeneously grained structure of austenite, *Acta Materialia*, 84 (2015) 1-8 , doi: 10.1016/j.actamat.2014.10.032.
- [20] R. L. Miller, Ultrafine-grained microstructures and mechanical properties of alloy steels, *Metallurgical Transactions*, 3 (4) (1972) 905-912, doi: 10.1007/BF02647665.
- [21] M. Merwin, Low-Carbon Manganese TRIP Steels, *Materials Science Forum*, 539 (2007) 4327-4332, doi: 10.4028/www.scientific.net/MSF.539-543.4327.
- [22] Xu,H.F, J. Zhao, W.Q.Cao, J.Shi, Wang.C.Y, Heat treatment effects on the microstructure and mechanical properties of a medium manganese steel (0.2C–5Mn), *Material Science Engineering A*, 532 (2012) 435-442, doi: 10.1016/j.msea.2011.11.009.
- [23] H. Aydin, E. Essadiqi, I.-H. Jung, S. Yue, Development of 3rd generation AHSS with medium Mn content alloying compositions, *Material. Science Engineering A*, 564 (2013) 501-508, doi: 10.1016/j.msea.2012.11.113.
- [24] R. Xiong, H. Peng, S. Wang, H. Si, Y. Wen, Effect of stacking fault energy on work hardening behaviors in Fe–Mn–Si–C high manganese steels by varying silicon and carbon contents, *Materials & Design*, 85 (2015) 707-714, , doi: 10.1016/j.matdes.2015.07.072.
- [25] B. L. Ennis, E. Jimenez-Melero, R. Mostert, B. Santillana, P. D. Lee, The role of aluminium in chemical and phase segregation in a TRIP-assisted dual phase steel, *Acta Materialia*, 115 (2016) 132-142, doi: 10.1016/j.actamat.2016.05.046.
- [26] C. Shao, W. Hui, Y. Zhang, X. Zhao, Y. Weng, Microstructure and mechanical properties of hot-rolled medium-Mn steel containing 3% aluminum, *Material Science Engineering A*, 682 (2017) 45-53, doi: 10.1016/j.msea.2016.11.036.
- [27] G. Mishra, A. K. Chandan, S. Kundu, Hot rolled and cold rolled medium manganese steel: Mechanical properties and microstructure, *Material Science Engineering A*, 701 (2017) 319-327, doi: 10.1016/j.msea.2017.06.088.
- [28] A. Arlazarov, M. Gouné, O. Bouaziz, A. Hazotte, G. Petitgand, P. Barges, Evolution of microstructure and mechanical properties of medium Mn steels during double annealing, *Material Science Engineering A* 542 (2012) 31-39, doi: 10.1016/j.msea.2012.02.024.
- [29] W. Hui, C. Shao, Y. Zhang, X. Zhao, Y. Weng, Microstructure and mechanical properties of medium Mn steel containing 3%Al processed by warm rolling, *Material Science Engineering A* 707 (2017) 501-510, doi: 10.1016/j.msea.2017.09.090.
- [30] H. Essoussi, S. Ettaqi, E. Essadiqi, The effect of alloying elements on the stacking fault energy of a TWIP steel, *Procedia Manufacturing*, 22 (2018) 129-134, doi: 10.1016/j.promfg.2018.03.020.
- [31] W. S. Yang, C. M. Wan, The influence of aluminium content to the stacking fault energy in Fe–Mn–Al–C alloy system, *Journal of Material Science*, 25 (3) (1990) 1821-1823, doi: 10.1007/BF01045392.

- [32] B. Sun, F. Fazeli, C. Scott, N. Brodusch, R. Gauvin, S. Yue, The influence of silicon additions on the deformation behavior of austenite-ferrite duplex medium manganese steels, *Acta Materialia*, 148 (2018) 249-262, doi: 10.1016/j.actamat.2018.02.005.
- [33] T. Furukawa, Dependence of strength-ductility characteristics on thermal history in lowcarbon, 5 wt-%Mn steels, *Materials Science and Technology*, 5 (5) (1989) 465-470, doi: 10.1179/mst.1989.5.5.465.
- [34] Z.P.Hu, Y.B.Xu, Y.Zou, R.D.K.Misra, Han.D.T, S.Q.Chen, D.Y.Hou, Effect of intercritical rolling temperature on microstructure-mechanical property relationship in a medium Mn-TRIP steel containing δ ferrite, *Materials Science and Engineering A*, 720 (2018) 1-10, doi: 10.1016/j.msea.2018.02.052.
- [35] M. Cai, Z. Li, Q. Chao, P. D. Hodgson, A Novel Mo and Nb Microalloyed Medium Mn TRIP Steel with Maximal Ultimate Strength and Moderate Ductility, *Metallurgical and Materials Transactions A*, 45 (12) (2014) 5624-5634, doi: 10.1007/s11661-014-2504-x.
- [36] S. Yan, T. Liang, J. Chen, T. Li, X. Liu, A novel Cu-Ni added medium Mn steel: Precipitation of Cu-rich particles and austenite reversed transformation occurring simultaneously during ART annealing, *Material Science Engineering A*, 746 (2019) 73-81, doi: 10.1016/j.msea.2019.01.014.
- [37] M. Calcagnotto, Y. Adachi, D. Ponge, D. Raabe, Deformation and fracture mechanisms in fine- and ultrafine-grained ferrite/martensite dual-phase steels and the effect of aging, *Acta Materialia*, 59 (2) (2011) 658-670, doi: 10.1016/j.actamat.2010.10.002.
- [38] C.C.Tasan, M.Diehl, D.Yan, M.Beshtold, F.Roters, L.Schemmann, C.Zheng, N.Peranio, D.Peranio, An Overview of Dual-Phase Steels: Advances in Microstructure-Oriented Processing and Micromechanically Guided Design, *Annual Review of Materials Research*, 45 (45) (2015), 391-431, doi: 10.1146/annurev-matsci-070214-021103.
- [39] B. Sun, F. Fazeli, C. Scott, B.Guo, C.Aranas, X.Chu, M.Jahazi, S.Yue, Microstructural characteristics and tensile behavior of medium manganese steels with different manganese additions, *Material Science Engineering A*, 729 (2018) 496-507, doi: 10.1016/j.msea.2018.04.115.
- [40] S. Lee, S.-J. Lee, S. Santhosh Kumar, K. Lee, B. C. D. Cooman, Localized Deformation in Multiphase, Ultra-Fine-Grained 6 Pct Mn Transformation-Induced Plasticity Steel, *Metallurgical and Materials Transactions A*, 42 (12) (2011) 3638-3651, doi: 10.1007/s11661-011-0636-9.
- [41] Z. H. Cai, H. Ding, Z. Y. Tang, R. D. K. Misra, Significance of control of austenite stability and transformation mechanisms in medium-manganese transformation-induced plasticity steel, *Material Science Engineering A*, 676 (2016) 289-293, doi: 10.1016/j.msea.2016.08.124.
- [42] X. G. Wang, L. Wang, M. X. Huang, Kinematic and thermal characteristics of Lüders and Portevin-Le Châtelier bands in a medium Mn transformation-induced plasticity steel, *Acta Materialia*, 124 (2017) 17-29, doi: 10.1016/j.actamat.2016.10.069.
- [43] S. Lee, S.-J. Lee, B. C. De Cooman, Austenite stability of ultrafine-grained transformation-induced plasticity steel with Mn partitioning, *Scripta Materialia*, 65 (3) (2011) 225-228, doi: 10.1016/j.scriptamat.2011.04.010.
- [44] Y. Ma, Medium-manganese steels processed by austenite-reverted-transformation annealing for automotive applications, *Materials Science and Technology*, 33 (15) (2017) 1713-1727, doi: 10.1080/02670836.2017.1312208.
- [45] B. C. De Cooman, *Automotive Steels*, Woodhead Publishing, 2017, pp. 317-385.
- [46] X. Zhang, G. Miyamoto, T. Kaneshita, Y. Yoshida, Y. Toji, T. Furuhashi, Growth mode of austenite during reversion from martensite in Fe-2Mn-1.5Si-0.3C alloy: A transition in kinetics and morphology, *Acta Materialia*, 154 (2018) 1-13, doi: 10.1016/j.actamat.2018.05.035.
- [47] J.-M. Jang, S.-J. Kim, N. H. Kang, K.-M. Cho, D.-W. Suh, Effects of annealing conditions on microstructure and mechanical properties of low carbon, manganese transformation-induced plasticity steel, *Metals and Materials International*, 15 (6) (2009) 909-916, doi: 10.1007/s12540-009-0909-7.
- [48] J. Hu, L.-X. Du, G.-S. Sun, H. Xie, R. D. K. Misra, The determining role of reversed austenite in enhancing toughness of a novel ultra-low carbon medium manganese high strength steel, *Scripta Materialia*, 104 (2015) 87-90, doi: 10.1016/j.scriptamat.2015.04.009.
- [49] A. Kozłowska, B. Grzegorzczak, M. Morawiec, A. Grajcar, Explanation of the PLC Effect in Advanced High-Strength Medium-Mn Steels A Review, *Materials*, 12 (24) (2019), doi: 10.3390/ma12244175.

- [50] W. Cao, C. Wang, C. Wang, J. Shi, M. Wang, H. Dong, Microstructures and mechanical properties of the third generation automobile steels fabricated by ART-annealing, *Science China Technological Sciences* 55 (7) (2012) 1814-1822, doi: 10.1007/s11431-012-4877-7.
- [51] H. Hu, Effect of solutes on Lüders strain in low-carbon sheet steels, *Metallurgical Transactions A* 14 (1) (1983) 85-91, doi: 10.1007/BF02643741.
- [52] T. Furukawa, H. Huang, O. Matsumura, Effects of carbon content on mechanical properties of 5%Mn steels exhibiting transformation induced plasticity, *Material Science Technology*, 10 (11) (1994) 964-970, doi: 10.1179/mst.1994.10.11.964.
- [53] Z. Li, Y. Tian, S. Kang, Z. Zheng, M. Liu, Effect of fast cooling rate on the microstructure and mechanical properties of low-carbon high-strength steel annealed in the intercritical region, *Journal of Wuhan University of Technology-Mater. Sci. Ed.*, 29 (3) (2014), 572-577, doi: 10.1007/s11595-014-0959-7.
- [54] S. Yu, Y. G. Deng, Z. Tao, R. D. K. Misra, Y. P. Yang, Effects of intercritical annealing time on microstructure, tensile properties, and cryogenic toughness of newly designed ultra-low C low Ni Medium-Mn steel, *Journal of Materials Research and Technology*, 32 (2024) 1245-1255, doi: 10.1016/j.jmrt.2024.07.222.
- [55] S. Lee, B. C. De Cooman, On the Selection of the Optimal Intercritical Annealing Temperature for Medium Mn TRIP Steel, *Metallurgical and Materials Transactions A*, 44 (11) (2013) 5018-5024, doi: 10.1007/s11661-013-1860-2.
- [56] J. Han, S.-J. Lee, J.-G. Jung, Y.-K. Lee, The effects of the initial martensite microstructure on the microstructure and tensile properties of intercritically annealed Fe-9Mn-0.05C steel, *Acta Materialia*, 78 (2014) 369-377, doi: 10.1016/j.actamat.2014.07.005.
- [57] X. Li, R. Song, N. Zhou, J. Li, An ultrahigh strength and enhanced ductility cold-rolled medium-Mn steel treated by intercritical annealing, *Scripta Materialia*, 154 (2018) 30-33, doi: 10.1016/j.scriptamat.2018.05.016.
- [58] J. Han, A. K. da Silva, D. Ponge, D. Raabe, Y.-K. Lee, S.-I. Lee, The effects of prior austenite grain boundaries and microstructural morphology on the impact toughness of intercritically annealed medium Mn steel, *Acta Materialia*, 122 (2017) 199-206, doi: 10.1016/j.actamat.2016.09.048.
- [59] R. Zhang, W. Q. Cao, Z. J. Peng, J. Shi, H. Dong, C. X. Huang, Intercritical rolling induced ultrafine microstructure and excellent mechanical properties of the medium-Mn steel, *Material Science Engineering A*, 583 (2013) 84-88, doi: 10.1016/j.msea.2013.06.067.
- [60] J. Han, Y.-K. Lee, The effects of the heating rate on the reverse transformation mechanism and the phase stability of reverted austenite in medium Mn steels, *Acta Materialia*, 67, (2014) 354-361, doi: 10.1016/j.actamat.2013.12.038.
- [61] Y.-K. Lee, J. Han, Current opinion in medium manganese steel, *Materials Science and Technology*, 31 (7) (2015) 843-856, doi: 10.1179/1743284714Y.0000000722.
- [62] W. Q. Cao, C. Wang, J. Shi, M. Q. Wang, W. J. Hui, H. Dong, Microstructure and mechanical properties of Fe-0.2C-5Mn steel processed by ART-annealing, *Material Science Engineering A*, 528 (22) (2011) 6661-6666, doi: 10.1016/j.msea.2011.05.039.
- [63] A. Kozłowska, B. Grzegorzczak, M. Staszuk, P. M. Nuckowski, A. Grajcar, Analysis of Plastic Deformation Instabilities at Elevated Temperatures in Hot-Rolled Medium-Mn Steel, *Materials* 12 (24) (2019) 4184, doi: 10.3390/ma12244184.
- [64] N. Ranc, W. Du, I. Ranc, D. Wagner, Experimental studies of Portevin-Le Chatelier plastic instabilities in carbon-manganese steels by infrared pyrometry, *Material Science Engineering A*, 663 (2016) 166-173, doi: 10.1016/j.msea.2016.03.096.
- [65] B. Sun, N. Vanderesse, F. Fazeli, C. Scott, P. Bocher, and M. Jahazi, Discontinuous strain-induced martensite transformation related to the Portevin-Le Chatelier effect in a medium manganese steel, *Scripta Materialia*, 133 (2017) 9-13, doi: 10.1016/j.scriptamat.2017.01.022.
- [66] A. K. Sachdev, Dynamic Strain Aging of Various Steels, *Metallurgical Transactions A*, 13 (10) (1982) 1793-1797, doi: 10.1007/BF02647835.
- [67] S. Lee, S.-J. Lee, S. Santhosh Kumar, K. Lee, B. C. D. Cooman, Localized Deformation in Multiphase, Ultra-Fine-Grained 6 Pct Mn Transformation-Induced Plasticity Steel, *Metallurgical Transactions A*, 42 (12) (2011) 3638-3651, doi: 10.1007/s11661-011-0636-9.

- [68] H. Fu, X. Chen, L. Zhang, Y. Tan, J. Xu, Y. Yan, The nonlinear analysis of Portevin-Le Chatelier (PLC) effect: An application to medium Mn steel, *Materials & Design*, 245 (2024), 113250, doi: 10.1016/j.matdes.2024.113250.
- [69] A. H. Cottrell, A note on the Portevin-Le Chatelier effect, *The London, Edinburgh, and Dublin Philosophical Magazine and Journal of Science*. 1953, pp. 829-832,
- [70] A. Yilmaz, The Portevin–Le Chatelier effect: a review of experimental findings, *Science and Technology of Advanced Materials* 12 (6) (2011) 063001, doi: 10.1088/1468-6996/12/6/063001.
- [71] F. Yang, H. Luo, C. Hu, E. Pu, H. Dong, Effects of intercritical annealing process on microstructures and tensile properties of cold-rolled 7Mn steel, *Material Science Engineering A*, 685 (2017) 115-122, doi: 10.1016/j.msea.2016.12.119.
- [72] J. H. Ryu, J. I. Kim, H. S. Kim, C.-S. Oh, H. K. D. H. Bhadeshia, D.-W. Suh, Austenite stability and heterogeneous deformation in fine-grained transformation-induced plasticity-assisted steel, *Scripta Materialia*, 68 (12) (2013) 933-936, doi: 10.1016/j.scriptamat.2013.02.026.
- [73] Y. Wang, Z. Ma, R. Song, S. Zhao, Z. Zhang, W. Huo, Correlation between cementite precipitation and Portevin-Le Chatelier effect in a hot-rolled medium Mn steel, *Materials Letters*, 258 (2020) 126796, doi: 10.1016/j.matlet.2019.126796.